

5._Sintering_time_optimazation_ 2018.pdf

by

Submission date: 10-Sep-2020 06:50PM (UTC+0700)

Submission ID: 1383573204

File name: 5._Sintering_time_optimazation_2018.pdf (2.29M)

Word count: 3943

Character count: 19982

PAPER

Sintering time optimization on red photoluminescence properties of manganese-doped boron carbon oxynitride (BCNO:Mn) phosphor

² To cite this article: Bebeh Wahid Nuryadin *et al* 2018 *Mater. Res. Express* **5** 046206

² View the [article online](#) for updates and enhancements.

Related content

- ³ [Spectroscopic investigation on BCNO-based phosphor: photoluminescence and long persistent phosphorescence](#)
Xiaofeng Liu, Song Ye, Guoping Dong et al.
- ⁴ [Structural refinement, bandgap analysis and optical properties of GdAlO₃ nanophosphors influenced by Dy³⁺ ions concentrations for white light emitting diode applications](#)
P K Jisha, Ramachandra Naik, S C Prashantha et al.
- ³ [Synthesis and photoluminescence of phosphorus AIBCO phosphors](#)
Yinghao Bai, Xiaoyu Song, Xuwen Xu et al.



PAPER


Sintering time optimization on red photoluminescence properties of manganese-doped boron carbon oxynitride (BCNO:Mn) phosphor

Bebeh Wahid Nuryadin¹ , Yuyu Suryani¹, Yuli Yuliani¹, Soni Setiadji², Ade Yeti Nuryantini³ and Ferry Iskandar^{4,5} RECEIVED
6 February 2018REVISED
5 March 2018ACCEPTED FOR PUBLICATION
5 April 2018PUBLISHED
20 April 2018¹ Department of Physics, UIN Sunan Gunung Djati Bandung, Jl. A H Nasution 105, Bandung, Indonesia 40614, Jl. A H Nasution 105, Bandung, Indonesia 40614² Department of Chemistry, UIN Sunan Gunung Djati Bandung, Jl. A H Nasution 105, Bandung, Indonesia 40614³ Department of Physics Education, UIN Sunan Gunung Djati Bandung Jl. A H Nasution 105, Bandung, Indonesia 40614⁴ Department of Physics, Institut Teknologi Bandung, Jl. Ganeca 10, Bandung, Indonesia 40132⁵ Research Center for Nanosciences and Nanotechnology, Institut Teknologi Bandung Jl. Ganeca 10, Bandung, Indonesia 40132E-mail: bebehwahid102@uinsgd.ac.id**Keywords:** BCNO:Mn phosphor materials, red photoluminescence, concentration quenching effect, sintering time optimization**Abstract**

The effect of sintering time to the transient nature and optimization of red photoluminescence manganese-doped boron carbon oxynitride (BCNO:Mn) phosphor was investigated. The BCNO:Mn samples were synthesized using a facile urea-assisted combustion route involving boric acid, citric acid, manganese salt and urea. The optimized intensity of the dual peak emission at 420 nm (blue emission) and 630 nm (red emission) in the photoluminescence (PL) spectrum could be achieved by controlling the sintering time of the BCNO:Mn. The BCNO:Mn samples in high-crystalline form was found to be in a cubic and hexagonal structure. Based on the PL analysis, it is suggested that the BCNO:Mn symmetric band at 630 nm can be attributed to the ${}^4T_1({}^4G) \rightarrow {}^6A_1({}^6S)$ transition absorption of Mn^{2+} ions into the hexagonal structure. Microstructure analysis showed an irregular and agglomerated shape of the BCNO:Mn sample.

1. Introduction

Boron carbon oxynitride (BCNO) materials are nitride semiconductors with an energy gap of >3 eV and have been widely developed due to their potential applications in lighting, bio-imaging, optoelectronic and luminescent devices [1–4]. Firstly, Ogi *et al* successfully developed a new type of boron nitride based phosphor, by preparing nitrogen and oxygen co-doped boron nitride (BCNO) phosphor through a urea combustion method [1]. BCNO phosphor has an emission spectrum in the range of visible light with higher quantum value results under UV light or blue LED exposure [1–4]. Until now, a great deal of research has been done that was focused on the control of the emission spectrum and quantum yield value of BCNO materials. For example, Wang *et al* [5] succeeded in optimizing the emission properties of BCNO materials from blue (387 nm) to dark yellow (571 nm) by changing the molar ratio of the carbon (C/B) or nitrogen (N/B) source to boron sources. Meanwhile, Kaihatsu *et al* [6] and Nuryadin *et al* [7] have examined the effects of different carbon sources, such as poly(ethyleneimine) and poly(ethylene glycol) with various molecular weights (MW) or citric acid, on the emission spectrum optimization of BCNO materials. In addition, Nuryadin *et al* [8], and Zhang *et al* [9] have induced red emission of BCNO materials with emission peaks at 581 nm to 620 nm using chemical and physical optimization. However, the induced red emission of BCNO still had low PL properties and quantum yields. Very recently, our group has synthesized a bright red emitting boron carbon oxynitride by doping with manganese (BCNO:Mn) with the emission peak at 600–650 nm [10]. The crystal structure, chemical composition, morphology and Mn^{2+} ion concentration influenced the photoluminescence properties of the BCNO. These parameters strongly depend on the preparation method and the experimental conditions, especially sintering time. Therefore, further research on the effect of sintering time on PL properties of BCNO:Mn is crucial in order to optimize PL performance and to understand the transient nature of the BCNO:Mn.

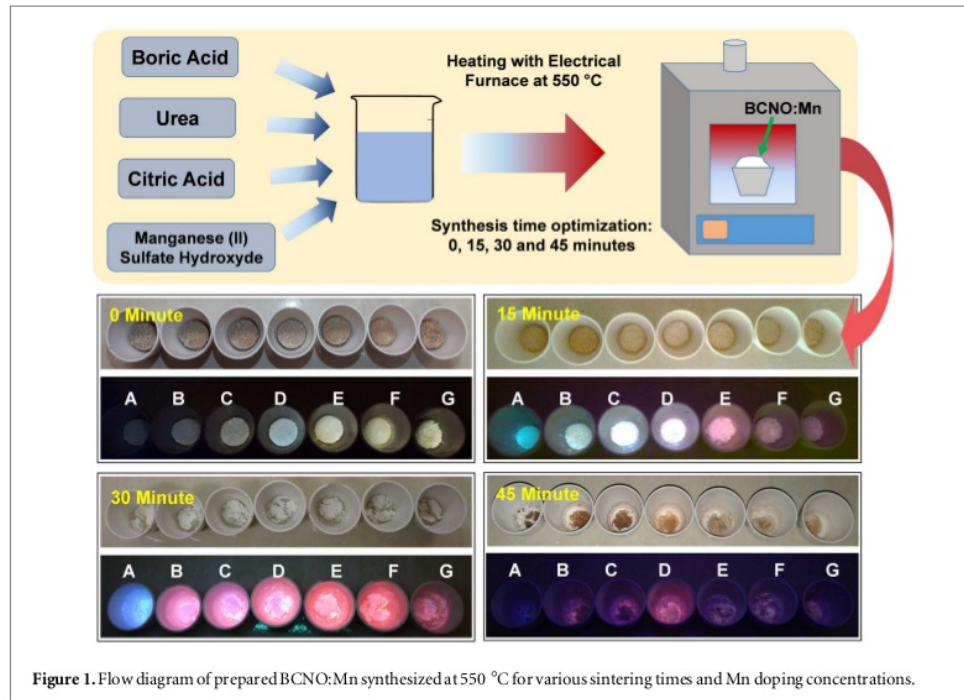

In this paper, we report the effect of sintering time to the transient nature and optimization of red photoluminescence manganese-doped boron carbon oxynitride (BCNO:Mn) phosphor synthesized by urea-assisted combustion route. By controlling the sintering time and doping concentration, optimization of the red emitting BCNO:Mn could be achieved. In addition, the crystal structure, photoluminescence (PL) spectra, decay curve, morphology and chemical composition of the synthesized BCNO:Mn have been investigated systematically. We believe that the optimization and understanding of BCNO:Mn formation can provide meaningful information for its application in optoelectronics, semiconductor lighting or panel displays.

2. Methods

2.1. Materials and synthesis

The urea-assisted combustion method is an important technique for the synthesis and processing of ceramics, metal oxides, catalysts, nanomaterial and composites. A flow diagram of the BCNO:Mn synthesis with different Mn^{2+} doping concentrations using the urea-assisted combustion method is shown in figure 1. The BCNO:Mn samples were synthesized using boric acid (H_3BO_3), urea ($(NH_2)_2CO$), citric acid ($C_6H_8O_7$) and manganese (II) sulfate monohydrate ($MnSO_4 \cdot H_2O$) as boron, nitrogen, carbon and manganese sources, respectively. The mass ratios of the boron, nitrogen and carbon sources were maintained constant at 5, 20 and 0.1, respectively. Furthermore, the manganese atom concentration was tuned by varying the Mn/B molar ratio from 0 to 2.84% mol/mol (table 1). Precursors were prepared by dissolving all raw materials in hot water under high speed stirring until becoming clear solutions. The prepared precursors were heated in an electrical furnace at 550 °C under variation of sintering time from 0, 15, 30 and 45 min. All samples were cooled naturally and powdered using mortar grinding for further analysis.

2.2. Materials characterization

The structures were characterized by x-ray diffraction (XRD, Philips Analytical PW 1710 BASED, PANalytical, the Netherlands) using Cu- $k\alpha$ as the x-ray source ($\lambda = 1.5 \text{ \AA}$). The particle morphology was observed by scanning electron microscopy (SEM; JCM-6000 NeoScope Benchtop, JEOL, Japan). The room-temperature photoluminescence (PL) spectra, excitation (PLE) spectra and luminescence decay curves (lifetime) of all BCNO:Mn phosphor samples were characterized using a Cary Eclipse spectrofluorophotometer (Agilent Ltd, Australia). The Fourier transform infrared (FT-infrared, Bruker Optics, Ettlingen, Germany) spectra with an Alpha Platinum ATR sampling module were used to determine the chemical bonding of the prepared samples.

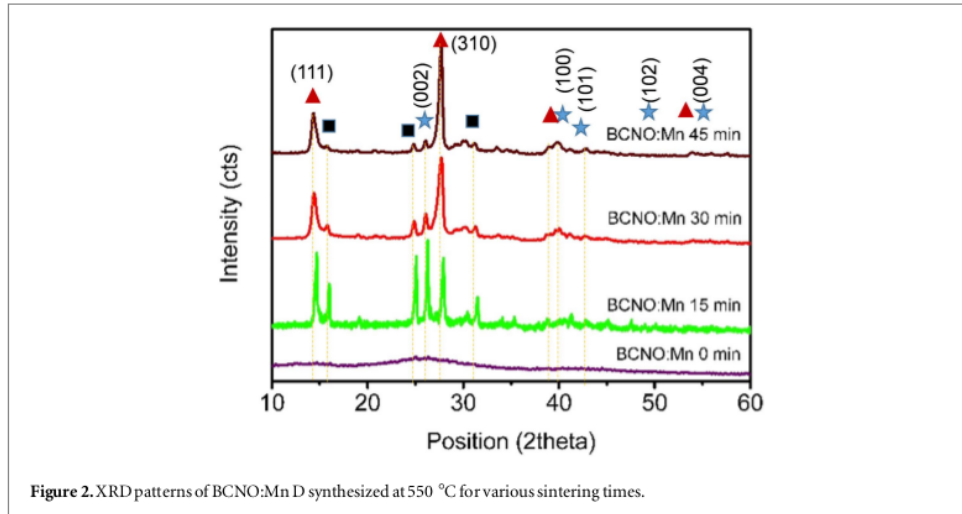


Figure 2. XRD patterns of BCNO:Mn D synthesized at 550 °C for various sintering times.


Table 1. The chemical composition of precursor for BCNO:Mn phosphor.

Sample	H ₃ BO ₃ (g)	Urea (g)	Citric Acid (g)	Mn/B (% mol/mol)
A				0%
B				0.18%
C				0.36%
D	0.5	2	0.01	0.71%
E				1.42%
F				2.13%
G				2.84%

3. Result and discussions

To determine the effect of sintering time on the crystal structure and phase purity, we characterized the BCNO:Mn D by x-ray diffractometry (XRD). Figure 2 shows the XRD patterns of the BCNO:Mn synthesized at 550 °C for various sintering times. The XRD patterns of the BCNO:Mn indicates the existence of pristine *h*-BN (blue star), boron oxide (red triangle) and graphitic carbon (black square). The formation of pristine *h*-BN (JCPDS no. 74-1978) [11], indicated by two broad peaks at 26.27° and 41.27°, yielded optimal intensity at 15 min, after which the intensity decreased with the increase of sintering time. The graphitic carbon peaks (JCPDS no. 75-1681) [12, 13] at 25.04° and 31.48° appear as imperfect decomposition of urea and become lower with the increase of sintering time. Besides that, the distinct and sharp peaks at 14.64°, 27.91° and 41.27° correspond to the crystal structure of *c*-B₂O₃ (JCPDS no. 06-0297) [14]. Observation showed a change of the structure of *h*-BN into *c*-B₂O₃ caused by the oxidation process in crystalline *h*-BN along with the increase in sintering time of the BCNO. Some researchers have shown that carbon and oxygen atoms can behave as impurity atoms in the crystal lattice of the BCNO. Thus, an increased sintering time causes chemical decomposition and the crystal structure becomes more perfect.

The morphology and the chemical bonding of the BCNO:Mn were measured using SEM and FTIR characterization. Figure 3(a) shows an SEM image of the prepared BCNO:Mn D synthesized at 550 °C. The image shows randomly agglomerated particles and irregular shapes with an average particle size of $\pm 5 \mu\text{m}$. This particle size is typical for phosphor powders used in lighting applications [7, 15, 16]. Figure 3(b) shows the typical FT-infrared spectra of BCNO:Mn material synthesized at 550 °C for various of sintering times in the range of 500–2500 cm^{-1} . The B–N stretching mode at $\sim 1400 \text{cm}^{-1}$, the B–C vibration peak at 1196cm^{-1} , and the B–N–B vibration peak at $\sim 790 \text{cm}^{-1}$ was observed in all of the BCNO:Mn samples [17, 18]. The absorption peaks at 560cm^{-1} , 650cm^{-1} , and 1500cm^{-1} correspond to B–O vibration bonds [19, 20]. The N–B–O absorption band is evident from $\sim 900 \text{cm}^{-1}$ to 1100cm^{-1} [9, 21]. In addition, the intensity of the N–B–O bonds increased with increasing sintering time, and the B–O absorption peak became clearer and its intensity increased caused by the decomposition and/or oxidation process as well as changes in the crystal structure of the BCNO:

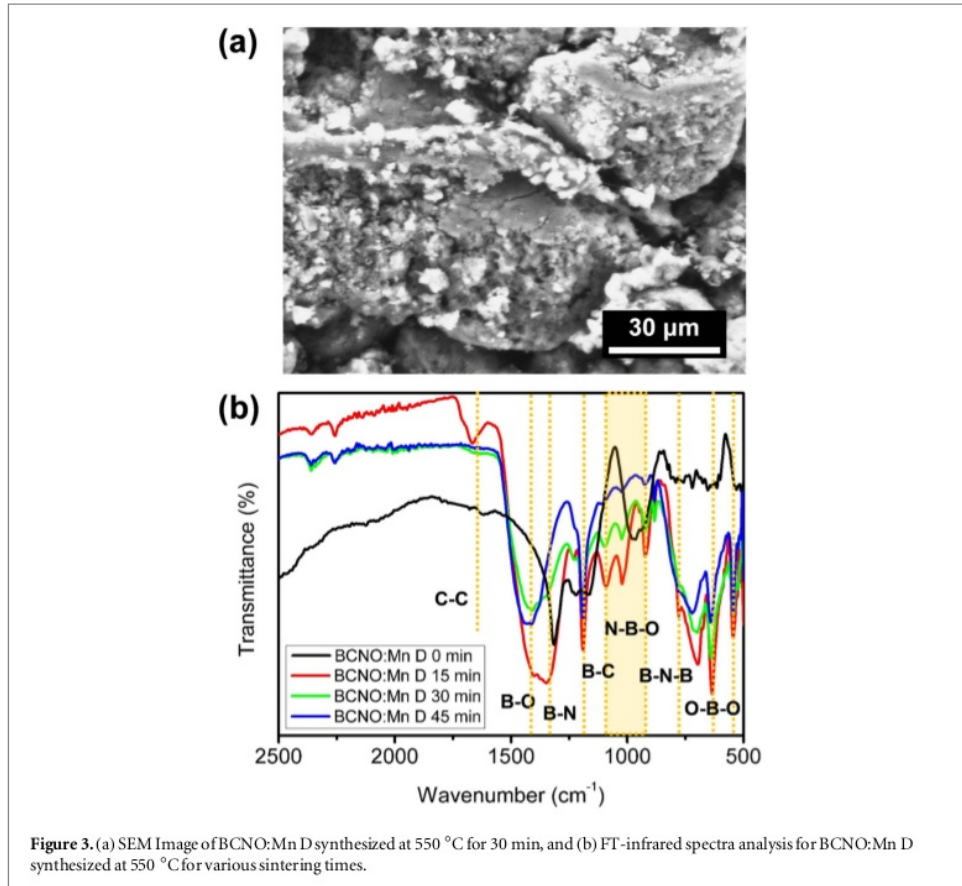

Mn. From the FT-infrared spectra, it can be concluded that the sintering time was involved ¹ in the chemical bonding and composition of the BCNO:Mn samples.

The photoluminescence (PL) spectra of the BCNO:Mn synthesized at 550 °C with various of sintering times and Mn²⁺ doping concentrations under UV light excitation at 365 nm, are shown in the figure 4. The spectra show that the PL properties of the BCNO:Mn exhibiting blue (~425 nm) and red emission (~630 nm) varied with different sintering times and Mn²⁺ concentrations. Previous research shows that blue emission of BCNO phosphor produced by the crystal structure of *h*-BN doped by oxygen and carbon [5–7]. Meanwhile, red emission was significantly appearing after BCNO material doped with Mn²⁺ ions. Nuryadin *et al* (2017) have shown that the red emission in BCNO:Mn²⁺ phosphor appears due to the associated Mn²⁺ ions in the *h*-BN hexagonal structure, and forms a new energy level in the BCNO electronic structure [10]. The BCNO:Mn synthesized for 0 min had a very low emission intensity. The emission intensity of the BCNO:Mn synthesized for 15 min showed an increase in comparison with the sample synthesized for 0 min, figure 4(a). Meanwhile, the BCNO:Mn synthesized for 30 min showed the highest red emission intensity (λ_{red} peak at 630 nm) compared with the prepared samples synthesized for 15 min and 45 min, figures 4(b)–(c). The decrease or increases in emission intensity can be ascribed to the crystal structure, chemical decomposition and doping quenching of the BCNO:Mn [7, 10, 22]. Observation showed that the PL intensity increased due to the increase in Mn²⁺ concentration that functions as a luminescence center of the red emission of the BCNO, as shown in figure 4(d). When the Mn²⁺ concentration increased, it caused the distance between the Mn²⁺ ions to become shorter and the energy transfer rates to get smaller. This facilitates the energy transfer between Mn²⁺ ions so that the energy transfer rate between the Mn²⁺ ions is equal to the emission of the Mn²⁺ ions and the emission intensity reaches its maximum value (radiative decays). At very high Mn²⁺ concentrations, the transfer energy between the Mn²⁺ ions is very tight and the energy transfer between the Mn²⁺ ions exceeds the emission levels. In other words, the Mn²⁺ ions will not be able to emit light, even though energy transfer occurs. Therefore, the excitation energy is absorbed by the crystal lattice transfer energy (non-radiative decays) and causes the emission intensity to decrease, known as the concentration quenching effect [10, 23, 24].

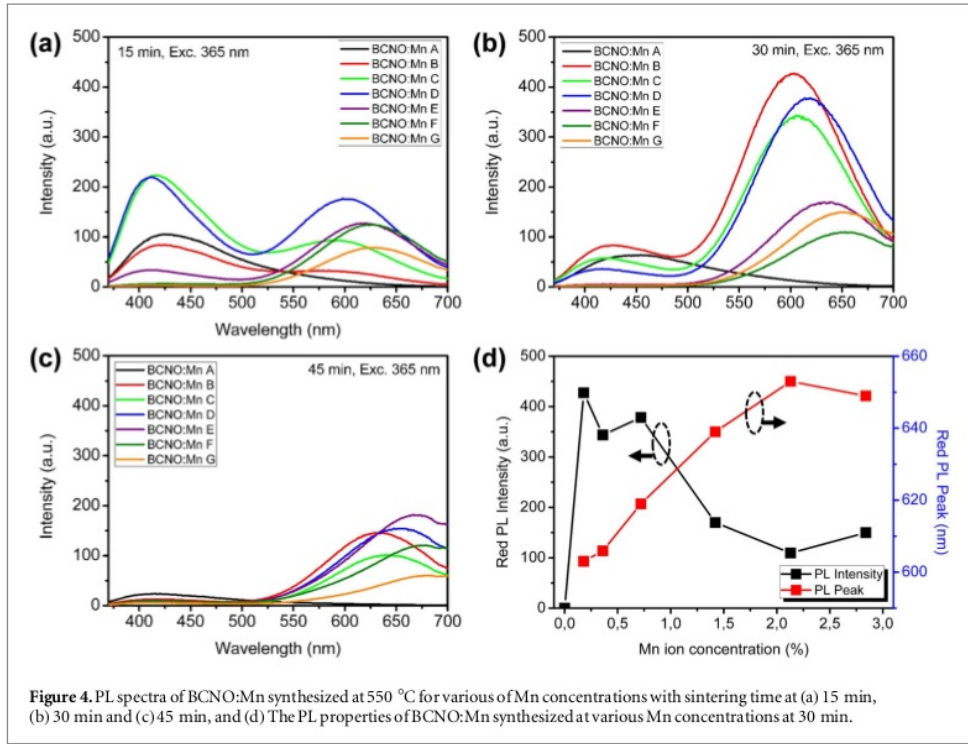


Figure 4. PL spectra of BCNO:Mn synthesized at 550 °C for various of Mn concentrations with sintering time at (a) 15 min, (b) 30 min and (c) 45 min, and (d) The PL properties of BCNO:Mn synthesized at various Mn concentrations at 30 min.


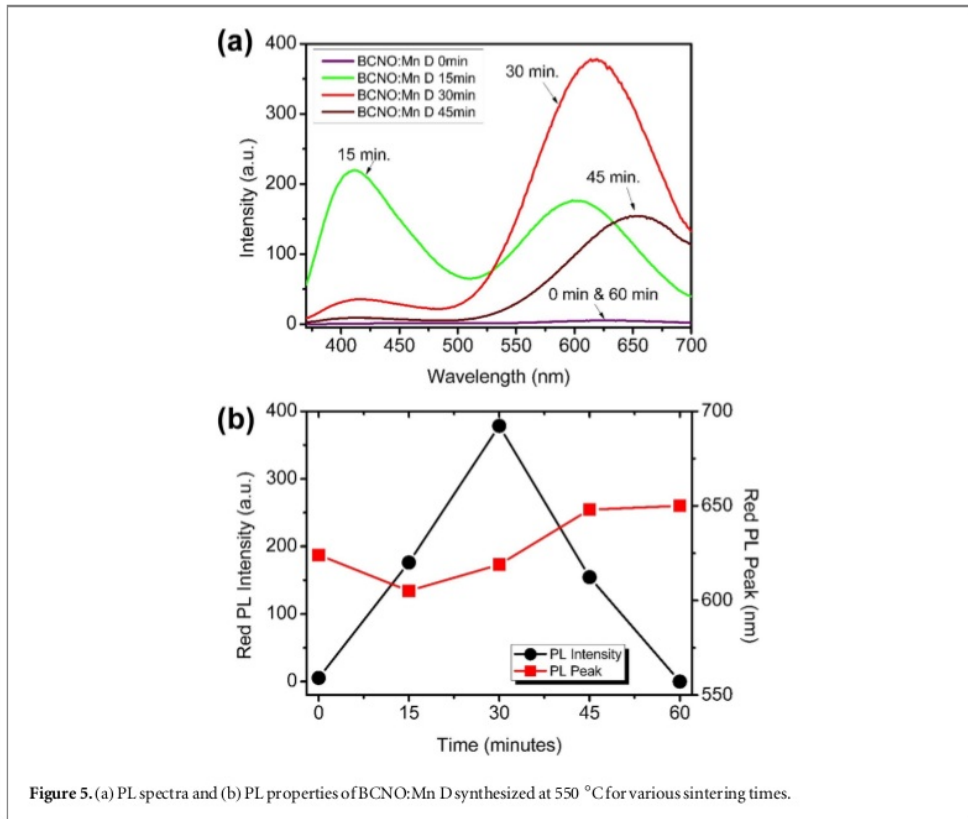


Figure 5. (a) PL spectra and (b) PL properties of BCNO:Mn D synthesized at 550 °C for various sintering times.

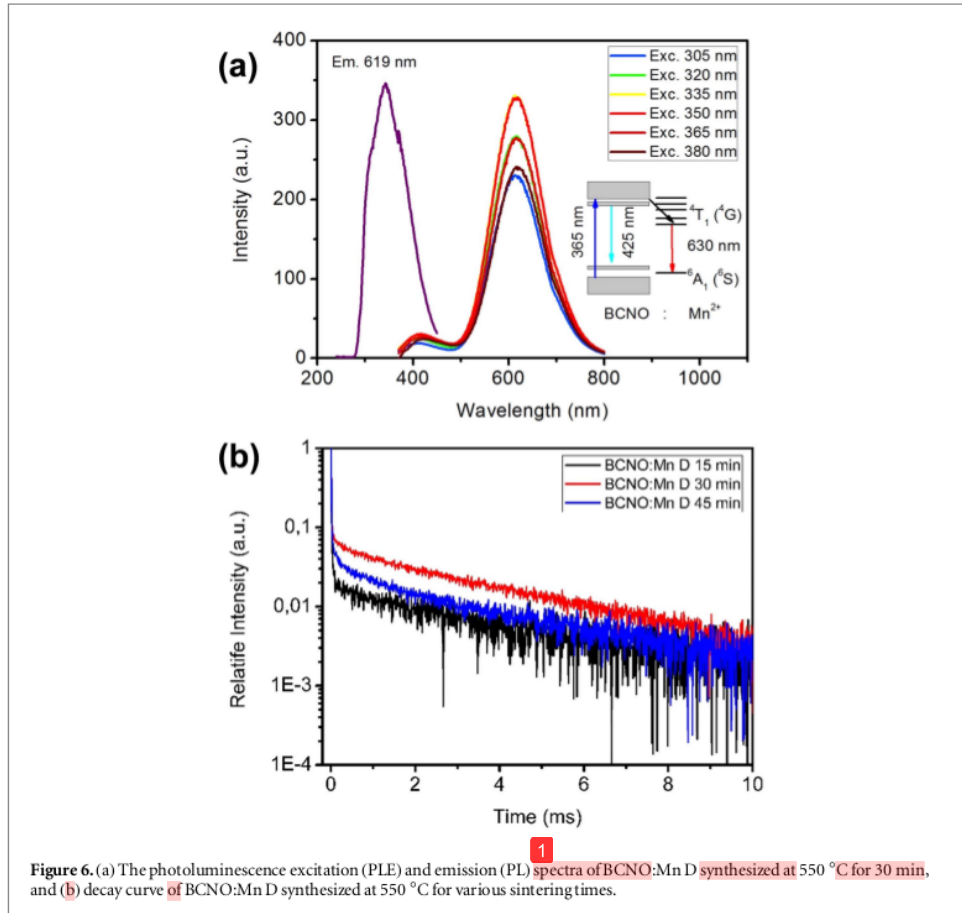

In addition, the red emission optimization of BCNO:Mn material remains consistent with the effect of sintering time observation on changes in the crystal structure and chemical composition due to decomposition and oxidation processes. For the synthesis time at 15 min, the BCNO crystals have been formed with predominant *h*-BN crystals so that the Mn²⁺ ions are associated with the hexagonal structure and produce the red emission energy level. However, due to the presence of undecomposed carbon impurities that produces non-radiative energy levels, so the red luminance intensity is low. For the time synthesis at 30 min, the presence of carbon impurities was reduced by thermal decomposition so that the intensity of the red emission was increased significantly. Meanwhile, for the time of synthesis of 45 min and 60 min, the process of decomposition and oxidation dominant place in the structure of *h*-BN, being B₂O₃, so that the Mn²⁺ ion is not in a hexagonal structure and cause the intensity of red emission decreased (even disappear) from BCNO:Mn²⁺, as shown at figure 5.

Figure 6(a) shows the photoluminescence excitation (PLE) and emission (PL) spectra of BCNO:Mn D synthesized at 550 °C for 30 min. The excitation spectra monitored at 630 nm show that the BCNO:Mn had an excitation wavelength in the near-UV light region, 300 nm to 420 nm. Excitation peaks of the BCNO:Mn D samples were observed at 350 nm and 370 nm. It is suggested that the peaks of 350 nm and 370 nm can be attributed to the electronic band transition (excitation) of the *h*-BN structure doped by oxygen, carbon, and crystal surface defects [7, 23, 25]. Thus, this red photoluminescence of BCNO:Mn phosphors can be well excited by near-UV light and blue LED. The decay curve profile related to the BCNO:Mn for various sintering times was estimated by monitoring the excitation peaks at 365 nm and the emission at 630 nm in accordance with the ⁴T₁(⁴G)–⁶A₁(⁶S) triplet emission band of the most intense of the Mn²⁺ ions, as can clearly be seen in figure 6(b). The decay curve measurements of the ⁴T₁(⁴G)–⁶A₁(⁶S) triplet transition fit with a double exponential profile for all prepared samples. Therefore, the lifetime of the ⁴T₁ state can be obtained by fitting the experimental decay curve with the double exponential function given below,

$$I_t = I_{01}e^{-\frac{t}{\tau_1}} + I_{02}e^{-\frac{t}{\tau_2}}$$

where, I , I_{01} and I_{02} are the emission intensity at t and $t = 0$ respectively, τ is the lifetime of the excited state [26, 27]. The lifetime values of the 4T_1 level of the BCNO:Mn were obtained by calculating the first exponential constant of the decay curves. The experimental lifetime (τ) values of the 4T_1 level were found to be 2.8 ms, 4.1 ms and 3.6 ms for the BCNO:Mn synthesized at 15 min, 30 min, and 45 min, respectively. The discrepancy in the experimental and calculated lifetime values is caused by non-radiative decays like multi-phonon relaxation and quenching effects caused by the Mn^{2+} ions.

4. Conclusions

In summary, the effect of sintering time of red emission manganese-doped boron carbon oxynitride (BCNO: Mn) phosphor on its PL properties was reported. The BCNO:Mn in high-crystalline form was found to be in a cubic and hexagonal structure. Microstructure analysis showed an irregular and agglomerated shape of the BCNO:Mn sample. The FTIR spectra showed that sintering time affects N-B-O, B-N, and B-O chemical bonding of BCNO:Mn. The optimum intensity of dual-peak emission at 420 nm and 630 nm in the photoluminescence (PL) spectrum could be optimized by controlling the sintering time of the BCNO:Mn. It is suggested that the BCNO:Mn symmetric band at 630 nm can be attributed to the ${}^4T_1({}^4G) \rightarrow {}^6A_1({}^6S)$ triplet transition absorption of the Mn^{2+} ions into the hexagonal structure.

Acknowledgments

This study was partly supported by a research grant from the *Penelitian Terapan dan Pengembangan—Integrasi Keilmuan* (PTIK/7340-1/2017), DIKTIS, Ministry of Religious Affairs and *Riset Desentralisasi PUPU* (Fiscal year 2017), Ministry of Research, Technology and Higher Education, Republic of Indonesia. B W N, F I and A Y N designed the research; Y S, Y Y, S S, and B W N performed the research and analysis; all authors contributed to the writing of the paper.

ORCID iDs

Bebek Wahid Nuryadin  <https://orcid.org/0000-0002-6653-4174>

Ade Yeti Nuryantini  <https://orcid.org/0000-0001-6382-7249>

Ferry Iskandar  <https://orcid.org/0000-0002-0464-0035>

References

- [1] Ogi T, Kaihatsu Y, Iskandar F, Wang W-N and Okuyama K 2008 Facile synthesis of new full-color-emitting BCNO phosphors with high quantum efficiency *Adv. Mater.* **20** 3235–8
- [2] Faryuni I D, Nuryadin B W, Iskandar F, Abdullah M, Ogi T and Okuyama K 2014 Synthesis and photoluminescence of BCNO/SiO₂ nanocomposite phosphor materials *J. Lumin.* **148** 165–8
- [3] Liu Q, Jiang P, Pu Z, Asiri A M, Al-Youbi A O and Sun X 2014 BCNO nanoparticles: a novel highly efficient fluorosensor for ultrarapid detection of Cu²⁺ *Sensors Actuators B Chem.* **194** 492–7
- [4] Iwasaki H, Ogi T, Iskandar F, Aishima K and Okuyama K 2015 Microwave synthesis of homogeneous and highly luminescent BCNO nanoparticles for the light emitting polymer materials *J. Lumin.* **166** 148–55
- [5] Wang W-N, Ogi T, Kaihatsu Y, Iskandar F and Okuyama K 2011 Novel rare-earth-free tunable-color-emitting BCNO phosphors *J. Mater. Chem.* **21** 5183
- [6] Kaihatsu Y, Wang W-N, Iskandar F, Ogi T and Okuyama K 2010 Effect of the carbon source on the luminescence properties of boron carbon oxynitride phosphor particles *J. Electrochem. Soc.* **157** J329
- [7] Nuryadin B W, Pratiwi T P, Iskandar F, Abdullah M, Khairurrijal K, Ogi T and Okuyama K 2014 Photoluminescence optimization of BCNO phosphors synthesized using citric acid as a carbon source *Adv. Powder Technol.* **25** 891–5
- [8] Nuryadin B W, Septia E C, Iskandar F, Ogi T, Okuyama K, Mikrajuddin A and Khairurrijal K 2014 Microwave-assisted solid state synthesis of red-emitting BCNO phosphor and its characteristics *Adv. Mater. Res.* **896** 464–7
- [9] Zhang X, Yan S, Cheng Y, Gao K, Lu Z, Meng F, Lin J, Xu X, Zhao J and Tang C 2013 Spectral properties of BCNO phosphor with wide range of excitation and emission *Mater. Lett.* **102–103** 102–5
- [10] Nuryadin B W, Permatasari F A, Nuryantini A Y, Faryuni I D, Abdullah M and Iskandar F 2017 A red emitting of manganese-doped boron carbon oxynitride (BCNO) phosphor materials: facile approach and photoluminescence properties *RSC Adv.* **7** 4161–6
- [11] Dwivedi J, Kumar P, Kedawat G and Gupta B K 2015 New emerging rare-earth free yellow emitting 2D BCNO nanophosphor for white light emitting diodes *New J. Chem.* **39** 5161–70
- [12] Ogi T, Iskandar F, Nandiyanto A B D, Wang W-N and Okuyama K 2012 Influence of polymer decomposition temperature on the formation of rare-earth free boron carbon oxynitride phosphors *J. Chem. Eng.* **45** 995–1000
- [13] Liu X, Ye S, Qiao Y, Dong G, Zhang Q and Qiu J 2009 Facile synthetic strategy for efficient and multi-color fluorescent BCNO nanocrystals *Chem. Commun.* **0** 4073–5
- [14] Yan S, Zhang X, Lu Z, Yu M, Xu X, Lin J, Fan Y, Zhang X, Meng F and Tang C 2014 Facile synthesis and photoluminescent properties of BCNO phosphors for white light emitting diodes application *Ceram. Int.* **40** 7617–20

- [15] Tran N T, You J P and Shi F G 2009 Effect of phosphor particle size on luminous efficacy of phosphor-converted white LED *J. Light. Technol.* **27** 5145–50
- [16] Koole R, Groeneveld E and Vanmaekelbergh D 2014 Size effects on semiconductor nanoparticles *Nanoparticles: Workhorses of Nanoscience* ed D Celso de Mello (Berlin Heidelberg: Springer) pp 13–51
- [17] Wang W-N, Kaihatsu Y, Iskandar F and Okuyama K 2009 Chemical and photoluminescence analyses of new carbon-based boron oxynitride phosphors *Mater. Res. Bull.* **44** 2099–102
- [18] Garvie L A J, Hubert H, Rez P, McMillan P F and Buseck P R 1999 BN_{0.5}O_{0.4}C_{0.1}: carbon- and oxygen-substituted hexagonal BN *J. Alloys Compd.* **290** 34–40
- [19] Suryamas A B, Munir M M, Ogi T and Okuyama K 2011 Intense green and yellow emissions from electrospun BCNO phosphor nanofibers *J. Mater. Chem.* **21** 12629
- [20] Singh D, Singh K, Singh G, Manupriya M, Mohan S, Arora M and Sharma G 2008 Optical and structural properties of ZnO–PbO–B₂O₃ and ZnO–PbO–B₂O₃–SiO₂ glasses *J. Phys. Condens. Matter* **20** 75228
- [21] Tang C, Bando Y, Zhi C and Golberg D 2007 Boron-oxygen luminescence centres in boron-nitrogen systems *Chem. Commun.* **0** 4599–601
- [22] Zhang X, Lu Z, Lin J, Fan Y, Li L, Xu X, Hu L, Meng F, Zhao J and Tang C 2012 Spectra properties of BCNO phosphor prepared by a two-step method at low sintering temperature *ECS J. Solid State Sci. Technol.* **2** R39–43
- [23] Kole A K and Kumbhakar P 2012 Effect of manganese doping on the photoluminescence characteristics of chemically synthesized zinc sulfide nanoparticles *Appl. Nanosci.* **2** 15–23
- [24] Sohn K-S, Cho B and Park H D 1999 Photoluminescence behavior of manganese-doped zinc silicate phosphors *J. Am. Ceram. Soc.* **84** 2779–84
- [25] Mancini G F, Ghigna P, Mozzati M C, Galinetto P, Makarova M, Syrnikov P, Jastrabik L and Trepakov V A 2014 Structural investigation of manganese doped SrTiO₃ single crystal and ceramic *Ferroelectrics* **463** 31–9
- [26] Liu X, Qiao Y, Dong G, Ye S, Zhu B, Zhuang Y and Qiu J 2009 BCNO-based long-persistent phosphor *J. Electrochem. Soc.* **156** P81
- [27] Zhang X, Lu Z, Lin J, Li L, Fan Y, Hu L, Xu X, Meng F, Zhao J and Tang C 2013 Luminescence properties of BCNO phosphor prepared by a green and simple method *Mater. Lett.* **94** 72–5

ORIGINALITY REPORT

4%

SIMILARITY INDEX

1%

INTERNET SOURCES

3%

PUBLICATIONS

0%

STUDENT PAPERS

PRIMARY SOURCES

1 Wei-Ning Wang, Takashi Ogi, Yutaka Kaihatsu, Ferry Iskandar, Kikuo Okuyama. "Novel rare-earth-free tunable-color-emitting BCNO phosphors", Journal of Materials Chemistry, 2011
Publication 1%

2 Gautam Gurung, Thilini K Ekanayaka, Andrew J Yost, Tula R Paudel. "Absorption enhancement by transition metal doping in ZnS", Materials Research Express, 2019
Publication 1%

3 Takashi Ogi, Yutaka Kaihatsu, Ferry Iskandar, Wei-Ning Wang, Kikuo Okuyama. "Facile Synthesis of New Full-Color-Emitting BCNO Phosphors with High Quantum Efficiency", Advanced Materials, 2008
Publication 1%

4 onlinelibrary.wiley.com
Internet Source 1%

5 export.arxiv.org
Internet Source

Exclude quotes On
Exclude bibliography On

Exclude matches < 1%